AD-A126 908 THE MOLECULAR WEIGHT DISTRIBUTION FOR MOLECULES 1/1
REQUIRING ROTATIONAL DIFF..(U) MASSACHUSETTS INST OF
TECH CAMBRIDGE DEPT OF MATERIALS SCIENC.. L H PEEBLES
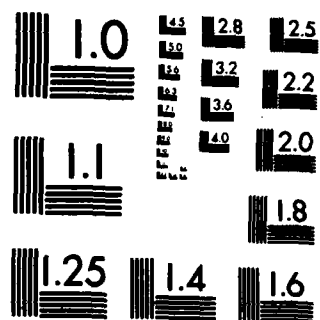UNCLASSIFIED OCT 82 TR-15 N00014-75-C-0542 F/G 20/8 NL

END
DATE
FILMED
5 83
DTIC

||||| 1.0 ‖ 4.5 ‖ 2.8 ‖ 2.5
           5.0
           5.6 ‖ 3.2 ‖ 2.2
           6.3
           ‖ 3.6
||||| 1.1   ‖ 4.0 ‖ 2.0

                    ‖ 1.8

||||| 1.25 ||||| 1.4 ||||| 1.6

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

①

OFFICE OF NAVAL RESEARCH

Contract N00014-75-C-0542

Task No. NR 356-534

Technical Report No. 15

The Molecular Weight Distribution for Molecules Requiring

Rotational Diffusion Prior to Reaction

by

L. H. PEEBLES, JR.

Prepared for Publication in MACROMOLECULES

Office of Naval Research
Detachment, Boston
495 Summer Street
Boston, MA   02210

and

Department of Materials Science and Engineering
Massachusetts Institure of Technology
Cambridge, MA   02139

October 1982

*Current address: Office of Naval Research
                   800 N. Quincy Street
                   Arlington, VA   22217

DTIC
ELECTE
APR 18 1983

S   D

B

83 04 15 115

REPORT DOCUMENTATION PAGE	READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report #15 2. GOVT ACCESSION NO. $AD\,A126908$	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) The Molecular Weight Distribution for Molecules Requiring Rotational Diffusion Prior to Reaction	5. TYPE OF REPORT & PERIOD COVERED
	6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) L. H. Peebles, Jr.	8. CONTRACT OR GRANT NUMBER(s) N00014-75-C-0542
9. PERFORMING ORGANIZATION NAME AND ADDRESS Massachusetts Institute of Technology Cambridge, MA 02139	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 356-534
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research, Code 413 800 N. Quincy Street Arlington, VA 22217	12. REPORT DATE October 1982
	13. NUMBER OF PAGES 18
14. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office)	15. SECURITY CLASS. (of this report)
	15a. DECLASSIFICATION/DOWNGRADING SCHEDULE

16. DISTRIBUTION STATEMENT (of this Report)

Approved for public release; distribution unlimited; reproduction in whole or in part is permitted for any purpose of the United States government.

17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, If different from Report)

18. SUPPLEMENTARY NOTES

19. KEY WORDS (Continue on reverse side if necessary and identify by block number)

Molecular weight distribution; diffusion; scaling law

20. ABSTRACT (Continue on reverse side if necessary and identify by block number)

The molecular weight distributions have been calculated for rigid rods which must rotate into a collinear conformation prior to reaction. The underlying assumptions include bimolecular reaction without by-product formation and a rotary diffusion parameter that is proportional to molecular length through the term $(i^{-N}+j^{-N})$ where i and j are rod lengths and N is an arbitrary parameter. To reduce the number of simultaneous differential equations that must be solved, an empirical scaling law is introduced which is independent of chain length. Essentially asymptotic values are obtained for number (over)

Introduction

In 1939 Flory announced the principle of equal reactivity of polymer chains (1). The principle maintains that the ability of a chain molecule to form larger molecules is independent of the chain length. The argument was very significant at that time for two reasons: First, the existence of high molecular weight polymers was considered by some to be improbable. These proponents argued that the high molecular weight species must have a higher diffusion constant, relative to the lower molecular weight species, which would eventually limit the extent of polymerization. Studies on condensation-type polymers with random coils demonstrated the general validity of the principle of equal reactivity (2). The second significant result was that the distribution of molecular weights could be readily calculated from kinetic parameters that were independent of chain length.

The major significant deviations from this principle seem to occur only with very low molecular weight species where inductive or polarization effects can be transmitted across a small molecule. Indeed, Lenz (3) cites a number of cases where the reactivity of a functional group on a difunctional monomer depends on whether or not the other functional group has reacted. Challa (4) showed a similar effect on the rate of polymerization of poly-(ethylene terephthalate) where the reactivity of the "monomer" bis-(β-hydroxyethyl) terephthalate differs from that of higher oligomers and polymer. Peebles and Wagner (5) examined the transesterification kinetics of dimethyl terephtalate and ethylene glycol in the presence of a catalyst.

They concluded that the second transesterification reaction was some three times faster than the first transesterification reaction. The overall transesterification of the terephthalate monomer must somehow involve some type of molecular transition state containing the catalyst because attempts to verify the faster transesterification reaction with the partly transesterified material resulted in absolutely no reaction (6). Thus, the documented "violations" of the principle of equal reactivity seems to be restricted to very small chain segments of random coil molecules.

Several calculations have been made to determine how departures from the principle of equal reactivity would influence the molecular weight distribution of a polymer. Nanda and Jain (7) assumed that the second order reaction constant for a condensation polymer was proportional to the molecular weight of the formed polymer through the relation $k(1+ \frac{\xi}{j} i)$, where k and ξ are constants and $\underline{i}$ is the number of monomers in a chain of length $\underline{i}$,

to obtain an analytical solution for the molecular weight distribution. Magat (8) developed simultaneous integral equations for stepwise polymerizations without termination for a number of conditions where the rate constant for propagation varied with chain length. His approaches are limited, however, in that the precise polymerization conditions must be specified before the equations can be evaluated.

A new series of stiff rod-like polymers (9) have recently been synthesized and characterized with a repeating unit of the form
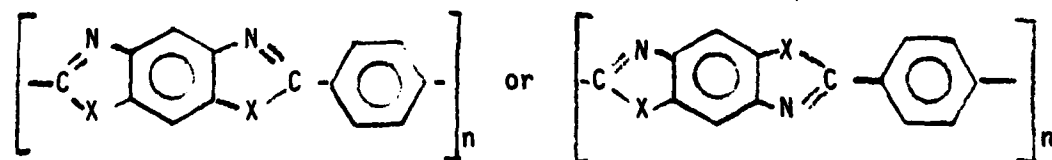
where the "X" atom can be oxygen, sulfur, or singly hydrated nitrogen.

The condensation of the functional groups

appears to occur simultaneously to form the benzobisoxazole because intermediate functionalities have not been detected by chemical or spectral means (9e). These observations suggest that the interacting molecules must be collinear (or nearly so) before reaction can take place. Furthermore, once reaction has commenced, the entire series of reactions to form the cyclic structure must occur quite rapidly. If such is the case, then the rate determining step is the ability of rods to rotate into a collinear configuration rather than the coupling step. Here the principle of equal reactivity is not violated; the reactivity of each end is independent of the length of the chain to which it is attached. The purpose of this paper is to calculate the molecular weight distribution for randomly oriented rod-like molecules which must diffuse or rotate into a collinear configuration prior to the coupling reaction.

Mathematical Development

The reaction between molecules of size i reacting with molecules of size j to form a molecule of size $i + j$ irreversibly and without by-product

$$x_i + x_j \longrightarrow x_{i+j} \tag{1}$$

is postulated to have a rate of formation proportional to $k\, c_{ij} x_i x_j$ where k is the specific second order rate constant for coupling, c_{ij} is a function of the molecular lengths i and j and is a measure of the ability of molecules to become collinear, and x_i, x_j are the concentrations of molecules of size i and j.

To simplify the notation, the constant k is adsorbed into the time derivative. Thus from eq (1), the rate of formation of x_i is given by

$$\dot{x}_i = \tfrac{1}{2} \sum_{j=1}^{i-1} c_{j,i-j} x_j x_{i-j} - x_i \sum_{j=1}^{\infty} c_{ij}\, x_j \tag{2}$$

The monomer x_1 is considered to react at the rate

$$\dot{x}_1 = - x_1 \sum_{j=1}^{\infty} c_{ij}\, x_j \tag{3}$$

These rate formulas can be summed to give the following time derivative functions

$$\sum_{i=1}^{\infty} i\, \dot{x}_i = 0 \qquad \text{line up} \tag{4}$$

since no by-product is formed.

$$\sum_{i=1}^{\infty} \dot{x} = - \tfrac{1}{2} \sum_{i=1}^{\infty} x_i \sum_{j=1}^{\infty} c_{ij} x_j \qquad \text{line up} \tag{5}$$

$$\sum_{i=1}^{\infty} i^2\, \dot{x}_i = \sum_{i=1}^{\infty} i\, x_i \sum_{j=1}^{\infty} j\, c_{ij}\, x_j \tag{6}$$

6

If the variable c_{ij} can be specified, then the molecular weight distribution and the moments of the distribution can in principal be determined by computer calculations.

Because many polymers have degrees of polmerization in excess of 100, and perhaps into the thousands or millions, it is not reasonable to solve the excessive number of simultaneous differential equations given by (2) and (3). However, if some type of scaling law can be found which will permit calculation of the distribution for a low number average molecular weight distributions, then computer calculations are feasible.

The generalized exponential distribution function

$$F(i,m,k) = my^{k/m} i^{k-1}[\exp(-yi^m)]/\Gamma(k/m) \qquad (7)$$

Gk cap Γ

$$W(i,m,k) = my^{(k+1)/m} i^k[\exp(-yi^m)]/\Gamma[(k+1)/m] \qquad (8)$$

where $\langle i\rangle_n = \Gamma[(k+1)/m]/y^{1/m}\Gamma(k/m)$,

can be rewritten in a scaling law form with $i/\langle i\rangle_n$ as the independent variable.

$$F(i,m,k)\langle i\rangle_n = \frac{mg^k}{\Gamma(k/m)}\left[\frac{i}{\langle i\rangle_n}\right]^{k-1} \exp\left[-(gi/\langle i\rangle_n)^m\right] \qquad (9)$$

$$W(i,m,k)\langle i\rangle_n = \frac{mg^k}{\Gamma(k/m)}\left[\frac{i}{\langle i\rangle_n}\right]^k \exp\left[-(gi/\langle i\rangle_n)^m\right] \qquad (10)$$

with $g = \{\Gamma[(k+1)/m]\}/\Gamma(k/m)$

This distribution is a generalized form of the Schulz distribution (m = 1), the Tung-Weibull distribution (k = m-1, k > 0), and a good approximation of the most probable distribution (m = k = 1) at large values of $\langle i\rangle_n$.

The next question to consider is the form of the function c_{ij} which determines the ability of the molecules to rotate into a collinear conformation. Doe and Edwards (9) suggest that the rotational diffusion constant of a rod

7

depends on $(\ln i)/i^3$ in dilute solution and higher inverse powers of i in more concentrated solutions, whereas Bird (10) suggests that the rotation of a rigid dumbbell depends on the square of the length (i^2). The assumption can then be made that if rod i were held fixed in space while rod j was allowed to rotate freely, then the rate of rotation would be proportional to j^{-N}, where N is an adjustable parameter. If rod j were held fixed and rod i allowed to rotate, the rate is proportional to i^{-N}. The overall average rate is then

$$c_{ij} = (i^{-N} + j^{-N})/2 \tag{11}$$

This equation can then be substituted into the set of simultaneous differential equations 2, – 6. The initial concentration of monomer, x_1 was selected to be unity. Initially, x_1 was taken as the independent variable. A set of K simultaneous differential equations $\dot{x}_i/\dot{x}_{ind}$, where $\dot{x}_{ind}$ is the change in concentration with time of the independent variable, was set up for solution by a computer. The value of K was selected to be large enough so that $\sum ix_i > .999$ over the range of integration considered. A Runga-Kutta method was used to obtain values of x_i, from i = ind to i = K. After each integration, an interger value of L = 0.8K was tested to see whether $Lx_L < 0.0005$. If the test failed, a larger value of K was selected, the program retreated to the results obtained on a previously performed integration, and computation continued. This procedure allowed only a small number of equations to be solved at the beginning of the solution, but as $<i>_n$ increased, more equations were solved, and hence more computer time required. Also, as $<i>_n$ increased, values of x_{ind} decreased and eventually became too small to permit reliable values of $\dot{x}_i/\dot{x}_{ind}$ to be computed as evidenced by fluctuations in x_{ind}. As x_{ind} approached this limiting value, a new independent variable was selected and concentrations of all i variables below x_{ind-1} were arbitrarily set to zero. Extensive testing of this procedure by choosing various values of i for the independent variable exhibited no effect on the calculated distribution provided that $x_{ind} < x_{max}$.

Results

Integration of eq's 2, 3, 5 and 6 were performed for integer values of N in eq 11 as a function of conversion. Values of $<i>_n$ varied from unity (initial condition) to $<i>_n$ values in excess of 50. From the x_i values so computed, values of $x_i<i>_n/\Sigma x_i$ were obtained. For all values of N used, except for $N = 0$ (the most probable distribution) the scaling law held to within the precision of the data when $<i>_n$ values exceeded ten. The results are presented in Fig.'s 1 and 2 for the distribution as a function of $i/<i>_n$ and in Fig. 3 for the heterogenity index $<i>_w/<i>_n$ as a function of conversion.

Discussion

The empirical observation that the scaling laws $F(i) <i>_n$ and $W(i)<i>_n$ are functions only of $i/<i>_n$ means that inexpensive computer calculations can be performed to evaluate these functions at small values of $<i>_n$. The function can then be used directly to evaluate the molecular weight distributions for large values of $<i>_n$. This technique can be used for other schemes relating kinetics to reactor designs, etc. where numerical calculations are required.

When the value of N in equation 11 is nonzero, the rate of polymerization $\Sigma \dot{x}_i$, eq 5, decreases with increasing conversion. As N increases, the rate of polymerization decreases at a faster rate. Both the scaled mole fraction and weight fraction distributions show a maximum in the range $i/<i>_n$ of 0.6-0.7, the maximum shifting to higher values with increasing N. The breadth of the distribution, however, becomes narrower, and reaches an asymptotic value at $<i>_n$ values of approximately 10. The application of these calculations to the observed distributions of Poly([benzo(1,2-d:5,4-d') bisoxazole-2,6 -diyl] -1,4-phenylene) has been discussed by Cotts and Berry (9e).

Acknowledgment

References and Notes

1. P. J. Flory, J. Am. Chem. Soc. 1936, 58, 1877

2. P. J. Flory, J. Am. Chem. Soc. 1939, 61, 3334; 1940, 62, 347

3. R. W. Lenz, "Organic Chemistry of Synthetic High Polymers" Interscience, New York, N.Y., 1967, p.

4. G. Challa, Makromol. Chem., 1960, 38, 105

5. L. H. Peebles, Jr. & W. S. Wagner, J. Phys. Chem, 1959, 63, 1206

6. Recent investigations by Wagner et al, private communication, 1981, suggest that the catalyst-monomer system follows third order kinetics, which tends to support involvement of a complex molecular transition state (5).

7. V. S. Nanda and S. C. Jain, J. Chem. Phys., 1968, 49, 1318

8. H. J. R. Maget, J. Polym. Sci, 1964, A2, 1281

9. a. J. F. Wolfe & F. E. Arnold, Macromolecules, 1981, 14, 909;
   b. F. J. Wolfe, B. H. Loo, F. E. Arnold ibid, p 915;
   c. E. W. Choe & S. N. Kim, ibid, p 920;
   d. R. E. Evers, F. E. Arnold, and T. E. Helminiak, ibid, p 925;
   e. D. B. Cotts & G. C. Berry, ibid, p 930;
   f. M. W. Wellman, W. W. Adams, R. A. Wolfe, D. S. Dudis, D. R. Wiff, & A. V. Fratini, ibid, p 935;
   g. S. -G. Chu, S. Venkatraman, G. C. Berry and Y. Einaga, ibid, p 939;
   h. W. J. Welsh, D. Bhavmik, and J. E. Mark, ibid, 947;
   i. D. B. Laumik, W. J. Welsh, H. H. Jaffe, & J. E. Mark, ibid, 951;
   j. R. R. Matheson, Jr. & P. J. Flory, ibid, 954;
   k. L. D. Bhavmik, H. H. Jaffe & J. E. Mark, ibid, 1125;
   l. S. R. Allen, A. G. Filippov, R. J. Farris, E. L. Thomas, C. P. Wong, G. C. Berry, & E. C. Chenevey, ibid, 1135.

10. M. Doi & S. F. Edwards, J. Chem. Soc., Faraday Trans II, 1978, 74, 918

11. R. B. Bird, O. Hassager, R. C. Armstrong, and C. F. Curtis, Dynamics of Polymer Liquids, Vol II, Chapt 11. John Wiley & Sons, New York 1977.

Legend for Figures

Figure 1. The scaled mole fraction of polymer as a function of $i/\langle i \rangle_n$ for various values of N in eq 11

Figure 2. The scaled weight fraction of polymer as a function of $i/\langle i \rangle_n$ for various values of N in eq 11

Figure 3. The heterogeneity index $\langle i \rangle_n/\langle i \rangle_n$ as a function of $\langle i \rangle_n$ and N.
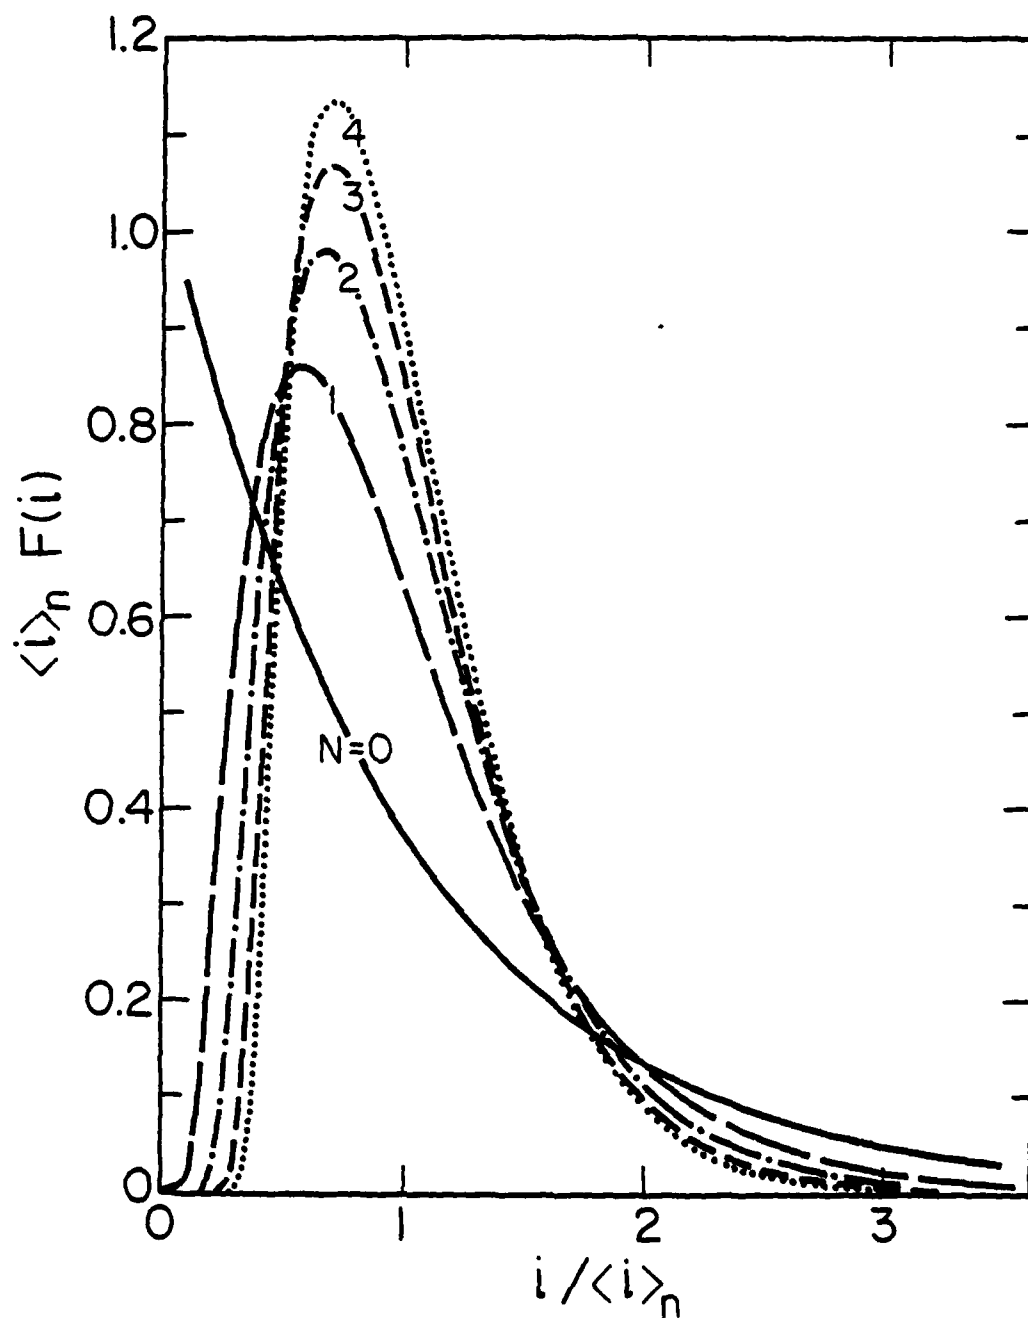
Fig 1

Fig 2
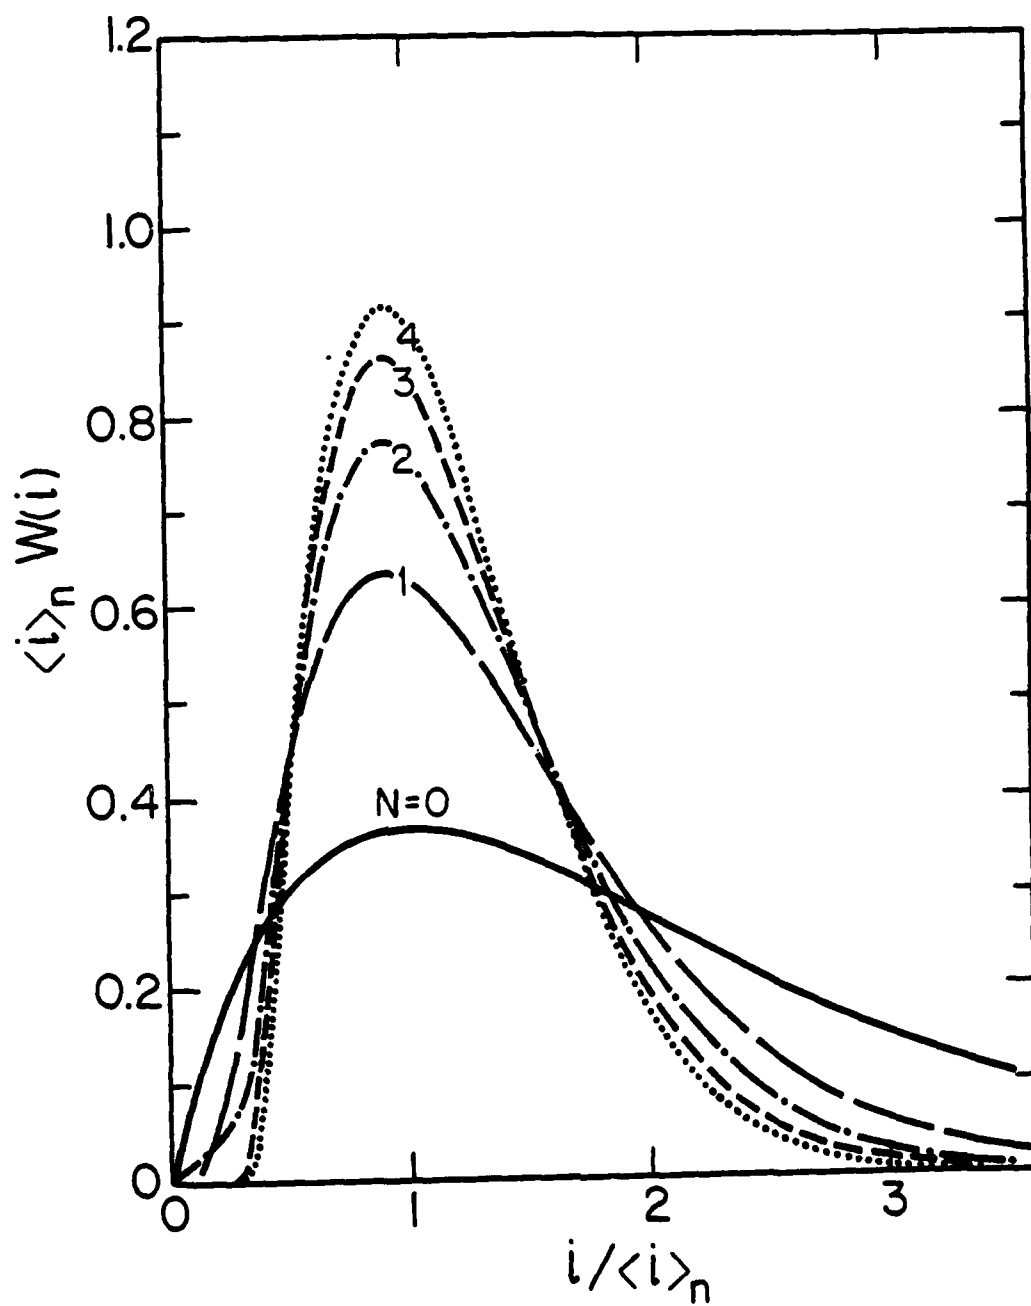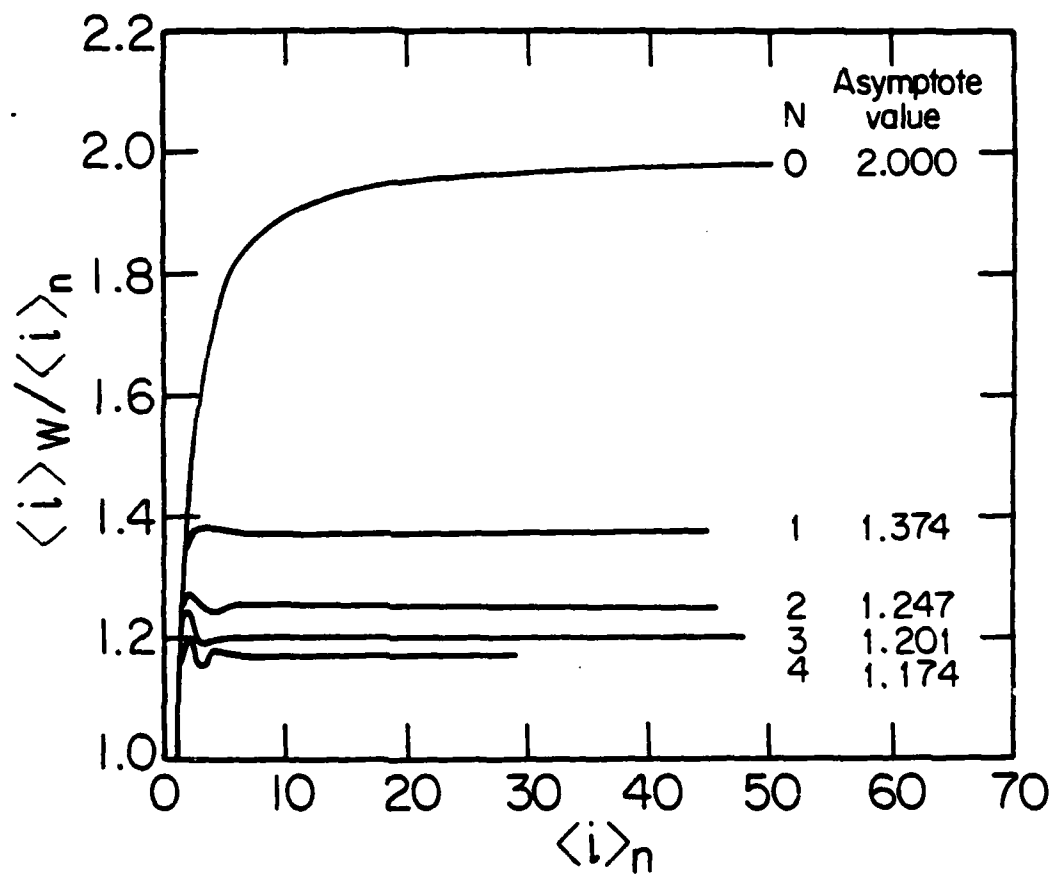
Fig 3

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	No. Copies		No. Copies

Office of Naval Research
Attn: Code -13
800 North Quincy Street
Arlington, Virginia 22217 — 2

ONR Pasadena Detachment
Attn: Dr. R. J. Marcus
1030 East Green Street
Pasadena, California 91106 — 1

Commander, Naval Air Systems Command
Attn: Code 310C (H. Rosenwasser)
Department of the Navy
Washington, D.C. 20360 — 1

Defense Technical Information Center
Building 5, Cameron Station
Alexandria, Virginia 22314 — 12

Dr. Fred Saalfeld
Chemistry Division, Code 6100
Naval Research Laboratory
Washington, D.C. 20375 — 1

U.S. Army Research Office
Attn: CRD-AA-IP
P. O. Box 12211
Research Triangle Park, N.C. 27709 — 1

Mr. Vincent Schaper
DTNSRDC Code 2803
Annapolis, Maryland 21402 — 1

Naval Ocean Systems Center
Attn: Dr. S. Yamamoto
Marine Sciences Division
San Diego, California 91232 — 1

Naval Ocean Systems Center
Attn: Mr. Joe McCartney
San Diego, California 92152 — 1

Naval Weapons Center
Attn: Dr. A. B. Amster,
Chemistry Division
China Lake, California 93555 — 1

Naval Civil Engineering Laboratory
Attn: Dr. R. W. Drisko
Port Hueneme, California 93401 — 1

Dean William Tolles
Naval Postgraduate School
Monterey, California 93940 — 1

Scientific Advisor
Commandant of the Marine Corps
(Code RD-1)
Washington, D.C. 20380 — 1

Naval Ship Research and Development
Center
Attn: Dr. G. Bosmajian, Applied
Chemistry Division
Annapolis, Maryland 21401 — 1

Mr. John Boyle
Materials Branch
Naval Ship Engineering Center
Philadelphia, Pennsylvania 19112

Mr. A. M. Anzalone
Administrative Librarian
PLASTEC/ARRADCOM
Bldg 3401
Dover, New Jersey 07801 — 1

TECHNICAL REPORT DISTRIBUTION LIST, 356A

	No. Copies		No. Copies
Dr. M. Broadhurst Bulk Properties Section National Bureau of Standards U. S. Department of Commerce Washington, D.C. 20234	2	Dr. K. D. Pae Department of Mechanics and Materials Science Rutgers University New Brunswick, New Jersey 08903	1
Naval Surface Weapons Center Attn: Dr. J. M. Augl, Dr. B. Hartman White Oak Silver Spring, Maryland 20910	1	NASA-Lewis Research Center Attn: Dr. T. T. Serofini, MS-49-1 2100 Brookpark Road Cleveland, Ohio 44135	1
Dr. G. Goodman Globe Union Incorporated 5757 North Green Bay Avenue Milwaukee, Wisconsin 53201	1	Dr. Charles H. Sherman Code TD 121 Naval Underwater Systems Center New London, Connecticut 06320	1
Professor Hatsuo Ishida Department of Macromolecular Science Case-Western Reserve University Cleveland, Ohio 44106	1	Dr. William Risen Department of Chemistry Brown University Providence, Rhode Island 02191	1
Dr. David Soong Department of Chemical Engineering University of California Berkeley, California 94720	1	Mr. Robert W. Jones Advanced Projects Manager Hughes Aircraft Company Mail Station D 132 Culver City, California 90230	1
Dr. Curtis W. Frank Department of Chemical Engineering Stanford University Stanford, California 94035	1	Dr. C. Giori IIT Research Institute 10 West 35 Street Chicago, Illinois 60616	1
Picatinny Arsenal Attn: A. M. Anzalone, Building 3401 SMUPA-FR-M-D Dover, New Jersey 07801	1	Dr. R. S. Roe Department of Materials Science and Metallurgical Engineering University of Cincinnatti Cincinnati, Ohio 45221	1
Dr. J. K. Gillham Department of Chemistry Princeton University Princeton, New Jersey 08540	1	Dr. Robert E. Cohen Chemical Engineering Department Massachusetts Institute of Technology Cambridge, Massachusetts 02139	1
Dr. E. Baer Department of Macromolecular Science Case Western Reserve University Cleveland, Ohio 44106	1	Dr. T. P. Conlon, Jr., Code 3622 Sandia Laboratories Sandia Corporation Albuquerque, New Mexico	1

TECHNICAL REPORT DISTRIBUTION LIST, 356A

	No. Copies		No. Copies
Dr. Martin Kaufman Code 38506 Naval Weapons Center China Lake, California 93555	1	Professor C. S. Paik Sung Department of Materials Sciences and Engineering Room 8-109 Massachusetts Institute of Technology Cambridge, Massachusetts 02139	1
Professor S. Senturia Department of Electrical Engineering Massachusetts Institute of Technology Cambridge, Massachusetts 02139	1	Professor Brian Newman Department of Mechanics and Materials Science	
Dr. T. J. Reinhart, Jr., Chief Composite and Fibrous Materials Branch Nonmetallic Materials Division Department of the Air Force Air Force Materials Laboratory (AFSC) Wright-Patterson AFB, Ohio 45433	1	Rutgers, The State University Piscataway, New Jersey 08854	1
		Dr. John Lundberg School of Textile Engineering Georgia Institute of Technology Atlanta, Georgia 30332	1
Dr. J. Lando Department of Macromolecular Science Case Western Reserve University Cleveland, Ohio 44106	1	Dr. D. R. Uhlmann Department of Materials Science Massachusetts Institute of Technology Cambridge, MA 02139	1
Dr. J. White Chemical and Metallurgical Engineering University of Tennessee Knoxville, Tennessee 37916	1		
Dr. J. A. Manson Materials Research Center Lehigh University Bethlehem, Pennsylvania 18015	1		
Dr. R. F. Helmreich Contract RD&E Dow Chemical Co. Midland, Michigan 48640	1		
Dr. R. S. Porter Department of Polymer Science and Engineering University of Massachusetts Amherst, Massachusetts 01002	1		
Professor Garth Wilkes Department of Chemical Engineering Virginia Polytechnic Institute and State University Blacksburg, Virginia 24061	1		